NAVAL POSTGRADUATE SCHOOL Monterey, California





THESIS

CINEMATOGRAPHIC STUDY OF AP/PBAA SANDWICH BURNERS IN A POSITIVE ACCELERATION FIELD

by

Wendell Earl Brown

Thesis Advisor:

D. W. Netzer

MAK 1972
Reproduced by
NATIONAL TECHNICAL
NFORMATION SERVICE
Springfield, Ve. 22151

Approved for public release; distribution unlimited.

40

	ROL DATA - R & D				
Security classification of title, body of abstract and indexing 1. ORIGINATING ACTIVITY (Corporate author)		the overall report is classified)			
		Unclassified			
Naval Postgraduate School Monterey, California 93940	26. GROUP	P			
Cinematographic Study of AP/PBAA in a Positive Acceleration					
Master's Thesis; March 1972					
5. AUTHORIS) (First name, middle initial, lest name)					
Wendell E. Brown					
S. REPORT DATE	78. TOTAL NO. OF PAGES	78. NO. OF REFS			
March 1972	40	14			
b. PROJETT NO.	94. ORIGINATOR'S REPORT	NUMBER(\$)			
с.	90. OTHER REPORT NO(5) (A	ny other numbers that may be assigned			
	this report)				
d.					
10. DISTRIBUTION STATEMENT					
Approved for public release; distr	ribution unlimite	ed.			
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY A	CTIVITY			
	Naval Postgrad Monterey, Cali	luate School .fornia 93940			
15. ABSTRACT					

Ammonium perchlorate/polybutadiene-acrylic acid (AP/PBAA) sandwich burners were burned in a combustion bomb. These were formed by bonding two polycrystalline AP wafers together with PBAA. Pressures were varied from 200 to 800 psig. Acceleration was either standard gravity or +100 g, i.e., 100 g directed normal and into the burning surface. Sandwich burns were recorded using high speed color motion pictures. It was found that binder/AP interactions cause transient burning rates which are sensitive to acceleration. For pressures below the lower deflagration limit (Pdl) of AP, the acceleration-induced flow of the binder onto the AP both inhibited AP decomposition and decreased the average burning rate. Sometimes the average burning rate remained unchanged from the base burning rate. For pressures above Pdl, acceleration-induced binder alow appears to affect the burning rate by mixing of the binder melt with the "active" AP.

DD FORM 1473 (PAGE 1)

S/N 0101-807-6811

Unclassified
Security Classification

Unclassified

Security Classification	LIN	K A	LINKB		-LINK C	
RET PURCE	ROLE	WT	ROLE	wT	POLE	₩T
Charles have been been as a						
Sandwich burners						
Solid propellant						
Burning rate						
Acceleration						
Photographic						
· ·						
	,					
•						
-						

DD FORM 1473 (BACK)

Unclassified
Security Classification

Cinematographic Study of AP/PBAA Sandwich Burners in a Positive Acceleration Field

by

Wendell Earl Brown Lieutenant, United States Navy B.S., United States Naval Academy, 1965

Submitted in partial fulfillment of the requirements for the degree of

MASTER OF SCIENCE IN AERONAUTICAL ENGINEERING

from the

Details of illustrations in this document may be better studied on microfiche

NAVAL POSTGRADUATE SCHOOL March 1972

Author

Approved by:

Thesis Advisor

/Chairman, Department of Aeronautical Engineering

Engineering

Academic Dean

ABSTRACT

Ammonium perchlorate/polybutadiene-acrylic acid (AP/PBAA) sandwich burners were burned in a combustion bomb. These were formed by bonding two polycrystalline AP wafers together with PBAA. Pressures were varied from 200 to 800 psig. Acceleration was either standard gravity or +100 g, i.e., 100 g directed normal and into the burning surface. Sandwich burns were recorded using high speed color motion pictures. It was found that binder/AP interactions cause transient burning rates which are sensitive to acceleration. For pressures below the lower deflagration limit (Pd1) of AP, the acceleration-induced flow of the binder onto the AP both inhibited AP decomposition and decreased the average burning rate. Sometimes the average burning rate remained unchanged from the base burning rate. For pressures above Pdl, acceleration-induced binder flow appears to affect the burning rate by mixing of the binder melt with the "active" AP.

TABLE OF CONTENTS

I.	INTRODUCTION	7		
II.	METHOD OF INVESTIGATION	10		
III.	EXPERIMENTAL PROCEDURES	11		
IV.	RESULTS AND DISCUSSION	16		
٧.	CONCLUSIONS	22		
VI.	RECOMMENDATIONS	23		
TABLE	S	24		
	ES			
REFER	ENCES	36		
JNITIAL DISTRIBUTION LIST 3				
FORM	DD 1473	39		

LIST OF TABLES

Table		Page
I.	SUMMARY OF AP(UHP)/PBAA SANDWICH TESTS	24
II.	SUMMARY OF AP(TCP)/PBAA SANDWICH TESTS	26
III.	SUMMARY OF AP(UHP)/PBAA SINGLE FACED	
	SANDWICH TEST	27
IV.	SUMMARY OF INCREMENTAL BURNING RATES FOR	
	AP(UHP)/PBAA SANDWICH TESTS	28

LIST OF FIGURES

Figur	re ·	Page
1.	Ammonium Perchlorate Wafer Forming Die	29
2.	Dimensioned Sandwich Purner	30
3.	Combustion Bomb End Cap with Sandwich	
	Burner Mounted	31
4.	ban Profiles of AP(UHP)/PBAA Sandwich Tests	32
5.	Burn Profiles of AP(TCP)/PBAA Sandwich Tests	34

ACKNOWLEDGEMENT

Grateful acknowledgement is given to Professor David
Netzer and Mr. Edward Michelson for their respective talents
and contributions without which this effort could not have
been successfully completed.

I. INTRODUCTION

Composite solid propellants subjected to an acceleration field normal and into the burning surface (i.e. positive "g") show an increase in the burning rate over that observed under standard gravity conditions [1, 2, 3]. This phenomenon is of concern to the design engine as the design of composite solid propellant rocket motors is dependent upon the consumption rate of the propellant enclosed within its walls.

The phenomenon of change in burning rate of composite propellants subjected to acceleration field has been studied by many investigators [3 through 10].

Past investigations have been directed more towards modeling acceleration effects upon metalized propellants with less effort being expended on nonmetalized composites. As a consequence of this, a satisfactory qualitative model for the acceleration-induced burning rate augmentation of metalized composite propellants exists, while models proposed for nonmetalized propellants seem either to be incorrect or are still unconfirmed by a sufficiently large amount of experimental effort.

Application of the phalanx flame model [8] seems to be incorrect because no evidence of preferential sub-surface reactions at the binder/ammonium perchlorate (AP) interface has been found in quench tests [10, 11, 12].

Glick [9] has proposed that the burning rate augmentation mechanism for nonmetalized composite propellants results from an effect of acceleration upon the diffusion burning of small pockets of fuel vapor as they leave the propellant and travel away from its surface. The validity of this model in acceleration fields of less than 1000 g is in doubt. For the vapor pockets to be consumed close enough to the surface of the propellant to cause augmentation, acceleration loadings would have to be in excess of those where augmentation is first observed [14].

A recent proposal for the mechanism responsible for composite solid propellant burning rate augmentation has been given by Cowles and Netzer [5]. It suggests an acceleration-induced forced mixing of molten binder with AP oxidizer crystals and/or AP surface melt.

The work in this thesis represents an attempt to determine the causes for the burning rate acceleration sensitivity of AP/Polybutadiene-acrylic acid (PBAA) nonmetalized composite propellants.

The method of investigation was one of high-speed motion picture photography of AP/PBAA sandwich burners. This method of investigation was chosen because previous work (Schroeder [6] and Pinney [7]) was relatively unproductive in obtaining good photographic data on nonmetalized composite propellants. Both of the above investigators identified the difficulties involved in obtaining photographs of the burning surface of nonmetalized propellants.

These difficulties encountered in attempting to extract photographic data from nonmetalized composites led to the idea of using a two-dimensional sandwich turner.

Two-dimensional sandwich burners allow good photographic analysis of the interface between AP oxidizer and PBAA fuel binder [10, 12, 13] and as such provide the basis for this investigation.

The validity of assuming that sandwich burner data describe the burning of three-dimensional composite propellants is questionable. However, sandwich burners allow photographic evaluation of the binder/AP interface during combustion. These interfacial conditions should be the same for sandwich burners and propellants.

II. METHOD OF INVESTIGATION

AP/PBAA sandwich burners formed by bonding two polycrystalline AP wafers together with PBAA, were burned in a combustion bomb at controlled pressures and acceleration environments. Runs were made at 200, 500, and 800 psig for both unaccelerated and the one hundred positive "g" condition. The AP used for the oxidizer was graded ultra high purity for one set of runs, and commercial with tricalcium phosphate (TCP) additive for the other set of runs. The burns (or runs) were recorded photographically as motion pictures, and from these motion pictures, burning rates and qualitative data were taken.

III. EXPERIMENTAL PROCEDURES

Sandwich burner preparation for this investigation started with the fabrication of the AP wafers from two lots of AP powder. Ultra high purity AP was provided by the Naval Weapons Center (NWC), China Lake (manufactured by American Potash and Chemical Corporation). This AP was 99.8 percent pure. The commercial grade AP (same manufacturer) was 99.4 percent pure with 0.2 percent TCP added as an anti-caking agent.

The ultra high purity AP had particle sizing ranging from 297 microns to 74 microns with 99.6 percent of it being larger than 104 microns. The commercial grade AP with TCP had particle sizing ranging from 500 microns to 74 microns. Micro-photographs showed that the TCP additive had a particle size of less than one micron.

The AP wafers were fabricated by weighing out 1.3 grams of AP and then placing it in a one-inch diameter die shown in Figure 1. This die was then placed in a twelve ton capacity Carver Laboratory hydraulic press and pressurized to 30,000 psi for twenty minutes. The completed polycrystalline AP wafer was then removed from the die. In all cases the wafers were whitish opaque in appearance. The completed wafers were weighed and measured and then density calculations were performed to ensure that they were of uniform construction and within two percent of the density of pure AP crystals.

AP wafers were then bonded together in pairs with PBAA binder to form the sandwich. This bonding was accomplished by thorough mixing of PBAA with EPON 828 as a catalyzer in the ratios of 84 percent by weight to 16 percent by weight respectively. The PBAA/EPON 828 mixture was uniformly smeared upon the face of one AP wafer; then the second AP wafer was placed over the first, sandwiching the PBAA. One-thousandth inch thick brass shim stock was placed between the AP wafers at three equally spaced points along their edges to ensure uniformity of binder thickness. During later portions of this investigation, small (15 gram) stainless steel weights were placed on the top AP wafer of the sandwich to further ensure binder thickness uniformity, and to reduce the tendency for the two wafers to slide over one another when the curing jar was evacuated. The sandwiches were then placed in a constant temperature oven at 72°C under a vacuum bell and were cured for a ninety-six hour period. During the first three hours of the cure period the vacuum bell was evacuated in excess of 28 inches of mercury.

Single-faced sandwiches (PBAA bonded to one AP wafer only) were constructed by placing the PBAA/EPON 828 mix-ture on a flat of Teflon or RTV and then placing an AP wafer over the top of the binder. These were cured in the same manner as described above, and were then lifted from the Teflon or RTV for cleaving.

Using a razor knife, the bonded AP/PBAA sandwiches were cleaved into small burners with dimensions of 0.45 inch high by 0.35 inch depth. These burners were then scraped to produce a squared face on all edges. Final dimensions of the scraped sandwich burners were 0.40 inch by 0.27 inch.

A pencil mark was made on the right-hand side AP wafer of the sandwich. This mark was made 0.15 inch up from the bottom edge of the burner. This pencil mark served to mark a focal point for the optical axis as well as to supply a reference point on the wafer from which photographic determination of burning rate could be made.

The sandwich burners were mounted with model-airplane cement on an aluminum pedestal as shown in Figure 2.

Ignition of the sandwich burners was accomplished using an 0.008-inch diameter nichrome resistance wire over the top of the burner. The wire was so oriented as to lie on the exposed binder at the top of the burner. A black gunpowder/cement/acetone mixture was then applied over the ignition wire to the top of the burner and allowed to dry. Preparation of a sandwich burner for a run was completed by this step. The completed sandwich burner mounted on the combustion bomb end cap is shown in Figure 3.

The sandwiches were burned in the horizontal position in the combustion bomb of the photographic centrifuge located in the Rocket Laboratory at the U. S. Naval Postgraduate School, Monterey, California. A description and figures of the photographic centrifuge and accompanying

Hycam motion picture camera together with information on their operation are given in Reference 6.

During runs the combustion bomb was purged with nitrogen to clear as much smoke as possible from the sandwich burner and to provide an inert atmosphere in which the burn took place.

Burning rates were taken from the films by projecting them onto a screen and measuring a length of burn over 0.4 to 0.6 of a second elapsed time. The top 0.075 inch of the sandwich was not included in the burning rate measurements in order to allow the burning rate to stabilize. age burning rates were calculated from the burn occuring between 0.075 inch from the sandwich top to 0.24 inch from the sandwich bottom. This distance was about 0.080 inch The projected screen distance was scaled to real distance by forming a ratio between the thickness of the projected image of the burner and the measured burner thickness. All burning distance measurements of the projected image could then be scaled to real dimensions using this ratio. The time elapsed between two points on the film was taken by counting the number of 0.001 second timing marks placed on the film edge by a Red Lake Laboratories Millimite TLG-4 timing oscillator. From the real distance burned and the actual time elapsed, burning rate was calculated.

When burning the sandwiches, sometimes the flame zone on one side of the binder would extend deeper into the burner than on the other side. On some runs this lowest

point would shift back and forth from one side of the binder to the other. All burning rate data were taken for the maximum point of advance of the flame zone.

The calculated burning rates are average burning rates for the zone over which the burn was observed.

All runs were made at a camera framing rate of 1500 pictures per second and at an "f" stop of 1.9. The optics arrangement gave a magnification of 1.4 on the film plane.

IV. RESULTS AND DISCUSSION

The experimental results of this investigation are summarized in Tables I, II, III, and IV.

The remarks in this section represent a composite of the general and detailed information derived from the films of all runs which could be considered successful.

Figures 4 and 5 show selected frames from runs made for varying "g" loadings, combustion bomb pressures, and AP grade.

No successful run for the commercial grade AP (with TCP) sandwiches burned at 800 psig and +100 g was obtained. All attempts to obtain data at these conditions were met with either unsuccessful ignition, or with the flame being extinguished within one-tenth inch of burn.

It is thus apparent that the burners fabricated from the commercial grade AP with TCP additive burned less readily than the ultra high purity AP sandwiches at all pressures and "g" loadings, other than the 200 psig runs. This might be due to a catalytic augmentation by the TCP or another impurity compound in the commercial grade AP. It is apparent that at 200 psig, which is below the low pressure deflagration limit (Pdl) of AP, there is some mechanism that causes the commercial grade AP with TCP to be consumed more readily than the ultra high purity AP.

At other pressures above P_{dl} for AP, the sandwiches made with ultra high purity AP show higher burning rates in all cases than the corresponding tests with sandwiches made with commercial grade AP with TCP conditioner. Burn profiles show that the ultra high purity AP is self-deflagrating while the commercial grade with TCP doesn't appear to self-deflagrate; rather it appears to thermally decompose. The scope of this study did not permit an investigation of why the AP with TCP was not self-deflagrating at pressures in excess of 350 psi.

The burning rates for AP with TCP at 500 psig and 0 g indicate that binder thickness apparently has little observable effect upon burning rates of AP/PBAA sandwich burners. This same observation also is made where the AP was graded ultra high purity and run conditions were 500 psig and +100 g. This phenomenon has also been observed by Jones and Strahle [13].

The flames for all the 200 psig, 0 g runs were laminar in nature. In the acceleration runs at 200 psig some flame turbulence was noted as a flickering of the flame from side to side. It was also observed from the increased width at the bottom of the burn profile that there was a tendency for the molten binder to be forced by the acceleration out past the binder AP interface and onto the AP. Binder flow onto the AP at +1 g conditions has been reported by Varney [10] and Jones and Strahle [13]. It is believed that the flame flickering seen in the +100 g runs at 200 psig was caused by

small pockets of oxidizer rich gases being liberated under the molten binder by thermal decomposition of the AP.

At pressures of 500 and 800 psig all flames were turbulent in appearance regardless of the acceleration field. In the case of the ultra high purity AP runs, this may be attributable to the self-deflagration of the AP.

In the case of the commercial grade AP it is believed that the increased burning rate liberates sufficient heat to thermally decompose the AP above the primary flame zone.

This decomposed oxidizer then diffuses outward from the wafer face creating a turbulent diffusion flame.

From Table I it may be seen that AP/PBAA sandwich burners made with ultra high purity polycrystalline AP wafers exhibit burning rate acceleration sensitivity. Below the Pdl of AP, average burning rate decreased with increasing acceleration. Above Pdl of AP, average burning rate increased with increasing acceleration. Sandwiches made with commercial grade AP with TCP additive showed no significant augmentation in average burning rate for accelerated conditions over those of no acceleration.

These results indicate that burning rate acceleration sensitivity of nonmetalized composite propellants is due in part to the interaction of the binder melt with the self-deflagrating AP. For pressures below the P_{dl} of AP (approximately 350 psig for pure AP and apparently greater than 800 psig for commercial grade AP with TCP), acceleration induced binder flow onto the AP inhibits AP decomposition

and the average burning rate decreases or remains unchanged. For pressu as above the Pdl of AP, acceleration induced binder flow appears to affect the burning rate by mixing of the binder melt with the "active" AP. The higher the pressure, the higher the binder "post" and the greater the binder/AP interaction (puddling, etc., see Figures 4 and 5). This could affect both heterogeneous and gas phase reaction rates. The average burning rate augmentations at 100 g of approximately ten percent at 500 and 800 psig (see Table I) are also in general agreement with propellant augmentation data [1, 5].

As indicated above, the burning rates reported in Tables I, II, and III are average burning rates. To obtain an estimate for the transient nature of the burn rate, the increment of burn over which the data was taken was split into two equal parts for 100 g and 0 g rung. This was done for ultra high purity AP/PBAA sandwich runs which were made at 500 psig and 800 psig. It was found that the burning rates at 0 g for both pressures increased between increments while those at 100 g decreased. For the 500 psig runs, the increase in the average incremental burning rate of the 0 g run did not exceed the average second increment burn rate for the 100 g run. For the 800 psig runs this was not found to be lower than the second increment average burning rate of the 0 g run. This points out the complexity involved in determing the mechanism(s) for acceleration induced burning rate augmentation of sandwich burners. The deflagration

rate of pure AP at pressures above its P_{dl} is a function of pressure. At 800 psig the AP is self-deflagrating at a higher rate than at 500 psig. As a consequence, the amount of binder not pyrolyzed and consumed by the AP oxidizer is greater in the 800 psig runs than in the 500 psig runs. Apparently a small amount of binder everflow onto the AP enhances the average burning rate [10, 13] of the sandwich. If excess binder builds up upon the surface of the AP it is possible that it acts as a heat sink and quenches the reaction.

The possible existence of preferred interfacial reactions between the binder and the AP was briefly considered. A sandwich was constructed in which only one AP wafer was cured to the binder. A matching AP wafer was placed firmly against the cured binder to form a sandwich. sandwich burner was identical to the normal burner except one side was "dewetted", i.e., it had a significantly different AP/binder interfacial condition on one side. This configuration should bias the reaction front toward interfacial reactions. A test was conducted with this sandwich at 500 psig and 0 g. No large order preferential burning down the unbonded interface was observed in the motion picture. However, it appeared that the unbonded AP wafer decomposed at a slightly faster rate than did the bonded wafer. In addition, the average burning rate for this sandwich was significantly greater than that obtained when both AP wafers were bonded to the PBAA (Table III).

The one test conducted is not adequate for drawing any strong conclusions.

The significance of the third place to the right of the decimal point in the average burning rate values is questionable. Although the measurements for burning rate calculations were taken from a projected image with a vernier caliper out to the thousandths inch place, the uncertainty of the exact location of the nadir of the burn prevents assigning too much significance to the third decimal place.

V. CONCLUSIONS

Test results indicate that burning rate acceleration sensitivity of AP/PBAA sandwich burners is due in part to the interaction of the binder melt with the self-deflagrating AP. For pressures below the Pdl of AP (approximately 350 psi for pure AP and apparently greater than 800 psi for commercial grade AP with TCP), acceleration induced binder flow onto the AP inhibits AP decomposition and the average burning rate decreases or remains unchanged. For pressures above the $P_{\mbox{\scriptsize dl}}$ of AP, acceleration induced binder flow appears to affect the burning rate by mixing of the binder melt with the "active" AP. The average burning rate augmentation, at +100 g, of approximately ten percent at 500 psig and 800 psig are also in general agreement with composite propellant augmentation data [1, 5]. At 800 psig the AP is self-deflagrating at a higher rate than at 500 psig. As a consequence, the amount of binder not pyrolyzed and consumed by the AP oxidizer is greater in the 800 psig runs than in the 500 psig runs. Apparently a small amount of binder overflow onto the AP enhances the average burning rate [10, 13] of the sandwich. If excess binder builds up upon the surface of the AP it is possible that it acts as a heat sink and quenches the reaction.

VI. RECOMMENDATIONS

It is recommended that more tests be made using the same run parameters as were used in this study. This would give an increased sampling of data, thereby increasing the level of confidence in the findings of this study. In addition, burning rates should be determined as a function of time for the entire run.

It is also suggested that studies should be pursued utilizing a wider range of binder thicknesses. This should be done to test for sensitivity of burning rate in acceleration environments to varying binder thicknesses.

Other tests should be made with different binder systems, such as polyurethane (PU), carboxyl-terminated polybutadiene (CTPB), etc. Such tests would reveal whether or not the acceleration-induced burning rate augmentation mechanism proposed in this study is applicable to other than AP/PBAA systems.

TABLE I

Summary of Data from AF(UHP)/PBAA Sandwich Tests

	Remarks	Small laminar flame burning only in the vicinity of the binder AP inter- face. Some evidence of AP pyroly- sis above the flame.	Small flame burning only in the vicinity of the binder AP interface. The flame appears more turbulent than the 200 psi, 0 g run, The AP appears to pyrolyze above the flame.	Burning with wide turbulent flame. AP decomposes below the level of the flame zone.	Burning with wide turbulent flame. AP decomposes below the level of the flame zone. Binder pools on the AP.	Burning with wide turbulent flame. AP decomposes below the level of the flame zone. Binder pools on the AP.	Burning with wide turbulent—flame. Can't see binder pooling of AP, how- ever greater width of flame at binder AP interface suggests binder overflow onto AP.
	Burn Profile						
	Binder Thickness (in)	• 003	• 003	900°	• 003	• 003	200.
•	Average Burn Rate (in/sec)	.07(9)	.06(4)	.17(7)	.20(9)	.19(5)	.20(2)
	Acceleration Loading (g)	0	100	0	100	100	100
	Pressure (psi)	200	200	909	500	900	200

TABLE I (cont)

Summary of Data from AP(UHP)/PBAA Sandwich-Tests

Remarks	Burning with wide turbulent flame. AP decomposes much faster than the binder, leaving a binder post stick—ing up. A lot of gray smoke from the AP was observed.	Burning with wide turbulent flame. Binder was observed to puddle on both AP wafers. Thick gray smoke from the AP was observed.
 Burn Profile	-	
Binder Thickness (in)	600.	\$000
Average Surn.Rate (in/sec)	,26(0)	.29(7)
rre Acceleration Loading E	0	100
Pressure (psi)	800	800
1		

TABLE II

MAA Sandwich Tests	Remarks	Burns with a small laminar flame only in the vicinity of the AP/binder inter- face. There is less evidence of AF pyrolysis than for the same run condi- tions with AP(UHP).	Burns with a small flame more turbullent than the above run. Burning occurs in the vicinity of the AP/binder interface. Binder appears to puddle near the center of the sandwich and puddle remains there during remainder of burn.	Burns with a turbulent flame. It appears that AP pyrolysis goes on some distance above the flame zone.	Burns with a turbulent flame. AP pyrolysis goes on for some distance above the flame zone.	Burns with a turbulent flame. Pyrolysis of the AP goes on for some distance above the flame zone. No binder puddling was observed.	Burns with a turbulant flame. AP pyrolysis appears to occur for some distance above the flame zone.	Had no successful runs for this condition.
Data from AP(TCP)/PBAA Sandwich Tests	Burn Profile		53	$\mathbf{\Xi}$	· 	23	\geq	3
	Binder Thickness (in)	• 005	• 003	. 002	7 00°	†00°	• 005	XXX
Summary of	Average Burn Rate (in/sec)	. 08(9)	.08(4)	.12(7)	.12(8)	.12(6)	.18(9)	X
	Acceleration Loading (g)	0	100	0	0	100	0	100
	Pressure (psi)	200	500	200	200	500	800	800

TABLE III

Summary of Data from AP(UHP)/PBAA Single Face Sandwich Test

Remarks	One might possibly see a preferential consuming of the unbonded side (right) AP wafer. It appears to decompose faster than the left side wafer. A great quantity of gray smoke is liberated from the surface of the AP. Burns with a wide turbulent flame.
Burn Profile	#
Binder Thickness (in)	• 003
Average Burn Rate (in/sec)	.19(9)
Acceleration Loading (g)	0
Pressure (psi)	500



TABLE IV

Average Burn Rate (in/sec) .17(4) .26(7) .29(6) .20(2) Summary of Incremental Burning Rates for AP(UHP)/PBAA Sandwich Tests Second Increment Average Burn Rate (in/sec) .18(3) .19(9) .31(1) .21(2) First Increment Average Burn Rate (in/sec) .16(5) .20(4) .22(4) .37(1) Acceleration Loading (g) 100 ,100 Pressure (psi) 500 500 800 800

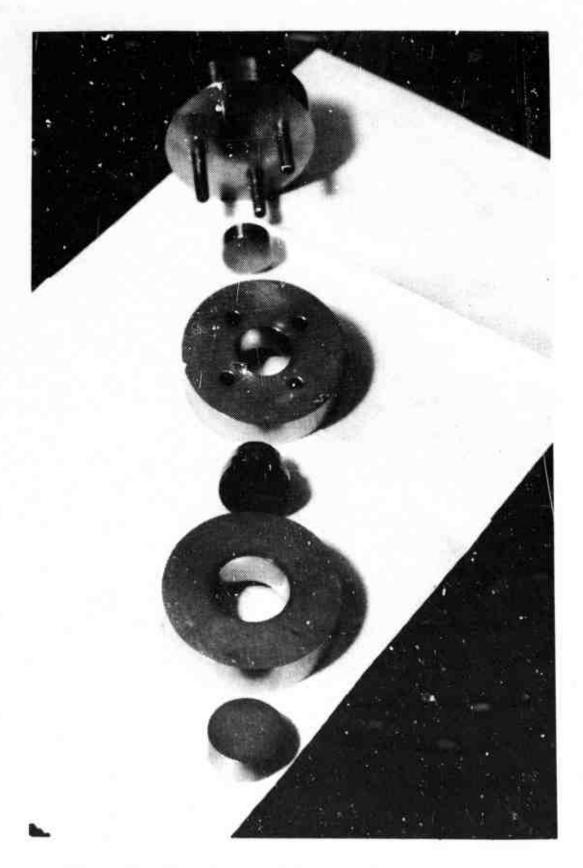


Figure 1. Ammonium Perchlorate Wafer Forming Die

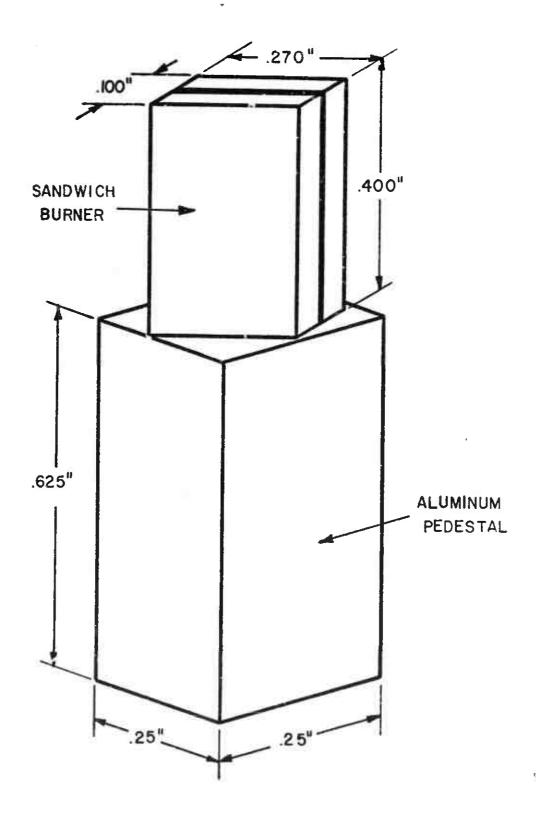


Figure 2. Dimensioned Sandwich Burner



Figure 3. Combustion Bomb End Cap With Sandwich Burner Mounted

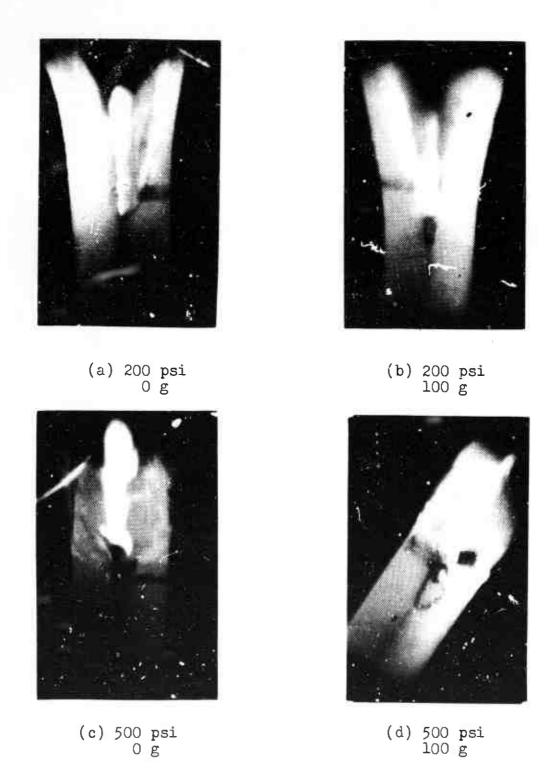


Figure 4. Burn Profiles of AP(UHP)/PBAA Sandwich Tests



(e) 800 psi 0 g



(f) 800 psi 100 g

Figure 4 (cont). Burn Profiles of AP(UHP)/PBAA Sandwich Tests

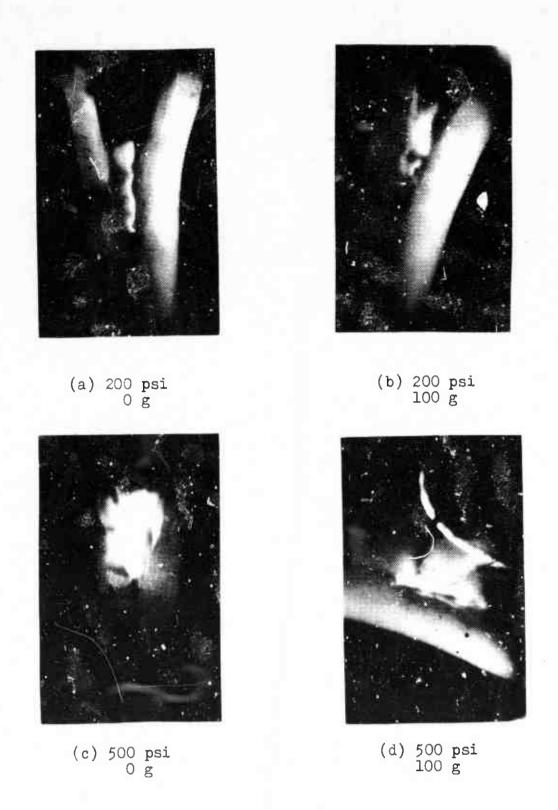


Figure 5. Burn Profiles of AP(TCP)/PBAA Sandwich Tests



(e) 800 psi 0 g

Figure 5 (cont). Burn Profiles of AP(TCP)/PBAA Sandwich Tests

REFERENCES

- 1. Sturm, E. J., A Study of the Burning Rates of Composite Solid Propellants in Acceleration Fields, Ph.D. Thesis, Naval Postgraduate School, Monterey, March 1968.
- 2. Northam, G. B. and Lucy, M. H., On the Effects of Acceleration Upon Solid Rocket Performance, paper presented at ICRPG/AIAA 3rd Solid Propulsion Conference, Atlantic City, New Jersey, 4-6 June, 1968. AIAA Paper No. 68-530.
- 3. Willoughby, P. G., Baker, K. L., and Hermsen, R. W., Photographic Study of Solid Propellants Burning in an Acceleration Environment, 13th Symposium (International) on Combustion.
- 4. Northam, G. B., <u>Acceleration-Induced Transient Burning-Rate Augmentation of an Aluminized Solid Rocket Propellant</u>, Ph.D. Thesis, Virginia Polytechnic Institute, 1969.
- Cowles, D. and Netzer, D., "The Effect of Acceleration on Composite Propellant Combustion," Comb. Sci. and Tech., Vol. 3, 1971.
- 6. Schroeder, R. C., Jr., <u>Cinematographic Study of Solid Propellant Combustion in an Acceleration Field</u>, <u>Master's Thesis</u>, <u>Naval Postgraduate School</u>, <u>Monterey</u>, <u>April 1970</u>.
- 7. Pinney, C. A., Cinematographic Study of Composite Solid Propellant Combustion in Positive and Negative Acceleration Fields, Master's Thesis, Naval Postgraduate School, Monterey, December 1970.
- 8. Sturm, E. J. and Reichenbach, R. E., A Study of the Burning Rates of Composite Solid Propellants in Acceleration Fields, Naval Postgraduate School Report NPS 57RV8121A, 5 December 1968.
- 9. Glick, R. L., An Analytical Study of the Effects of Radial Acceleration Upon the Combustion Mechanism of Solid Propellant, Contract NAS7-406, NASA Report No. 66218, Thiokol Report No. 42-66, 1966.
- 10. Varney, M. A., An Experimental Investigation of the Burning Mechanisms of Ammonium Perchlorate Composite Solid Propellants, Ph.D. Thesis, Georgia Institute of Technology, May 1970.

- 11. Boggs, T. L., Derr, R. L., and Beckstead, M. W., "Surface Structure of Ammonium Perchlorate Composite Propellants," AIAA Journal, Vol. 8, No. 2, 1968.
- 12. Hightower, J. D. and Price, E. W., "Experimental Studies Relating to the Combustion Mechanism of Composite Propellants," Astronautica Acta, Vol. 14, 1968.
- 13. Jones, H. E. and Strahle, W. C., "A Motion Picture Study of AP Sandwich Combustion," 8th JANNAF Combustion Meeting, CPIA Publication 220, Vol. 1, November 1971.
- 14. Atlantic Research Corporation, Second Annual Technical Report, An Optical Bomb Study of the Combustion of Solid Propellants in High Acceleration Fields, by M. K. King and E. T. McHale, 1969.